



# Oil Shale Pyrolysis Reaction Model by Solving Ordinary Differential Equation Approach

**Shahrul Azman Zainal Abidin**

**Ahmad Junaidi Jalaludin**

**Mohd Nazri Fuad**

PETRONAS Group Technology Solution

**Dr. Omar Bekri**

CHAPEM Consultants, Morocco

© 2007 PETROLIAM NASIONAL BERHAD (PETRONAS)

All rights reserved. No part of this document may be reproduced, stored in a retrieval system or transmitted in any form or by any means (electronic, mechanical, photocopying, recording or otherwise) without the permission of the copyright owner.



## PRESENTATION OUTLINE




**Introduction**

Methodology

Results & Future Studies

Questions



## INTRODUCTION

- Previous study focused on linearization method in solving the ordinary differential equation representing oil shale decomposition reaction
- Results are to be compared to other mathematical models
- Maintains the following representation for oil shale decomposition:



- Aim is to obtain conversion parameters for the decomposition reaction.
- Current study is to compare with fourth order Runge-Kutta method

## INTRODUCTION: Runge-Kutta Method

- One of the methods in solving ordinary differential equations
- Solution of Initial Value Problem of ODE in the form of:

$$- \cdot y_i(x_o) = y_{i_o} \quad i = 1, \dots, N$$

$$- \cdot \frac{dy_i(x)}{dx} = f_i(x, y_1, \dots, y_N)$$

$$- \cdot y_{n+1} = y_n + \frac{h}{6}(k_1 + 2k_2 + 2k_3 + k_4) + O(h^5)$$

where

$$k_1 = f(x_n, y_n)$$

$$k_2 = f\left(x_n + \frac{h}{2}, y_n + \frac{h}{2}k_1\right)$$

$$k_3 = f\left(x_n + \frac{h}{2}, y_n + \frac{h}{2}k_2\right)$$

$$k_4 = f(x_n + h, y_n + hk_3)$$

- Iterative procedure



## PRESENTATION OUTLINE



Introduction

**Methodology**

Results & Future Studies

Questions




# EXPERIMENTAL METHODOLOGY


The following parameters are to be determined from the model:

Model parameters	Symbol	Unit
Activation energy for kerogen decomposition	$E_1$	J/mol
Frequency factor for kerogen decomposition	$k_{10}$	$s^{-1}$
Activation energy for bitumen decomposition	$E_2$	J/mol
Frequency factor for bitumen decomposition	$k_{20}$	$s^{-1}$
Fraction of kerogen decomposition into oil and gas at each heating rate	$f_1$	

The TGA results at three different heating rates:

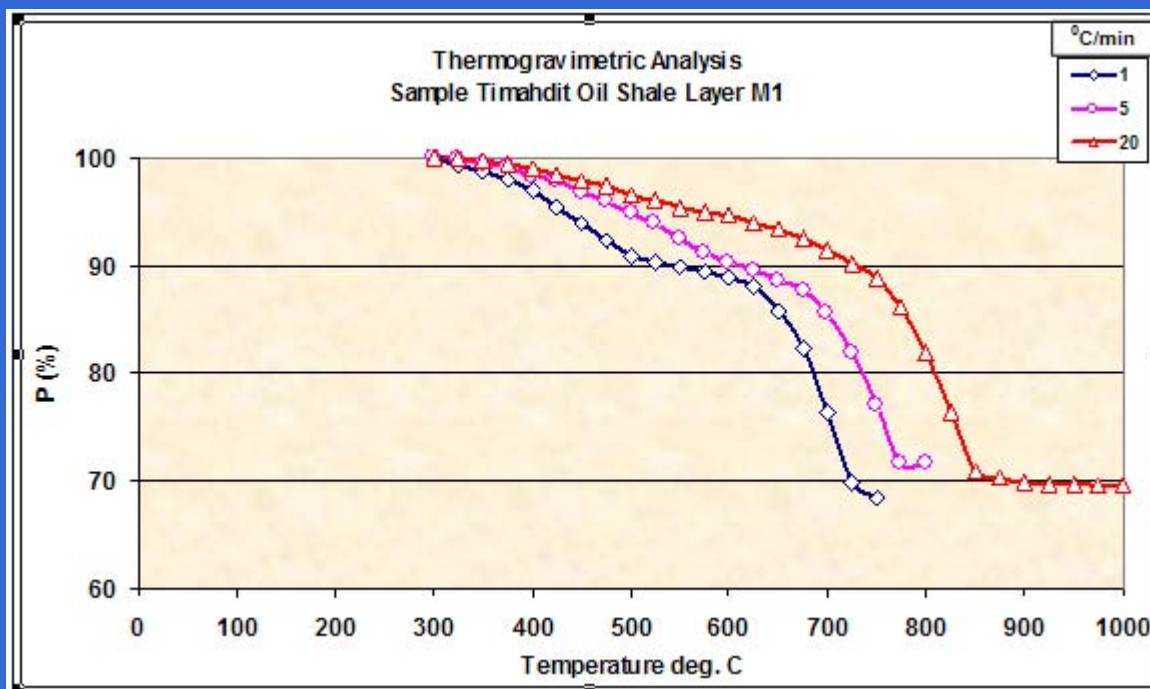

# EXPERIMENTAL METHODOLOGY

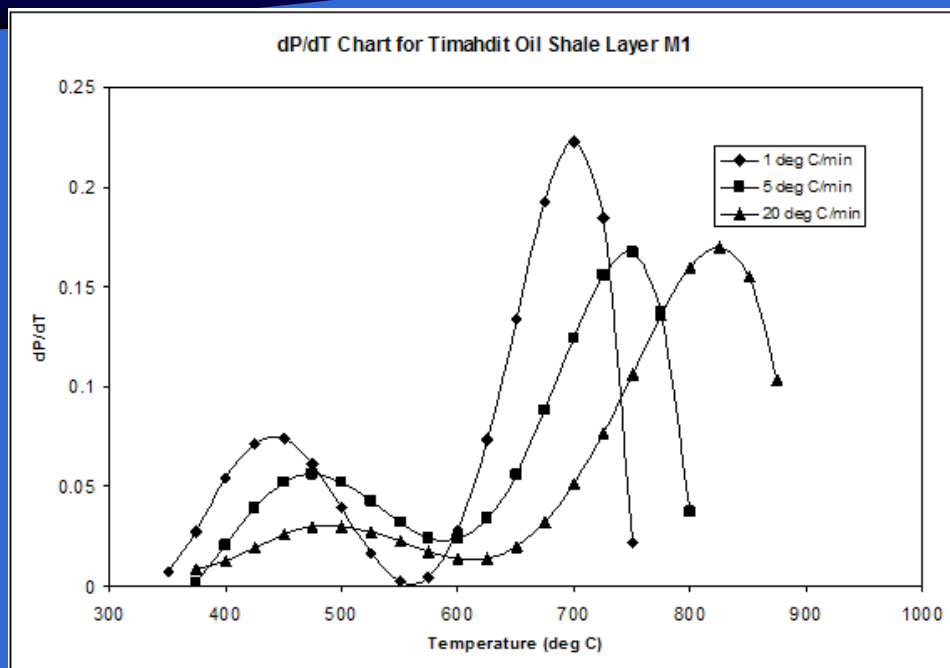

The differential curve of the weight loss over temperature graph at three different heating rates. This curve will provide the estimates for the boundary conditions and initial value to solve the ODE. The table below shows the typical decomposition ranges for different components based on differential curves

Component	Temperature Range (°C)
Kerogen	300-500
Bitumen	440-650
Dolomite	650-750
Calcite	720-850

An important assumption in the above decomposition reactions is that bitumen concentration is neglected in the reaction for kerogen and likewise kerogen concentration is neglected for the decomposition of bitumen.

## MATHEMATICAL MODELLING

- The two ODEs in this study are for kerogen decomposition and:

$$\frac{dP}{dT} = \frac{\exp\left(-\frac{E_1}{RT} + \ln(Mo \cdot f_1 \cdot k_{10}) - \left(\frac{k_{10} \cdot RT^2}{E_1} \cdot e^{-E_1/RT}\right) \cdot \frac{1}{V}\right)}{-V}$$

- Bitumen decomposition:

$$\frac{dP}{dT} = \frac{1}{V} k_{20} \cdot e^{-E_2/RT} \cdot (P - P_0)$$

- The TGA results provided the data for boundary conditions and initial values to solve the ODE representing the decomposition reaction
- Developed solver based on the fourth-order Runge-Kutta implementation with fixed step size control.
- Output from the solver will tabulate values of sample mass fraction (weight loss) versus temperature at particular heating rates.

## MATHEMATICAL MODELLING


The following table represents the values that were independently determined to provide initial values to solve the ODEs. The temperature ranges for kerogen and bitumen decomposition were determined by analysing the corresponding  $dP/dT$  curve

<b>Fixed parameters for the model</b>	<b>Value</b>
Initial fraction of organic material in the shale, $M_o$ (%)	15.28
Kerogen decomposition temperature range	300 – 441.07 °C at 1 °C/min 300 – 474.17 °C at 5 °C/min 325 – 489.20 °C at 20 °C/min
Bitumen decomposition temperature range	441.07 – 560.20 °C at 1 °C/min 474.17 – 588.53 °C at 5 °C/min 489.20 – 611.23 °C at 20 °C/min
Sample mass fraction where organic matter decomposition terminates, $P_o$ (%)	68.5 at 1 °C/min 71.5 at 5 °C/min 69.6 at 20 °C/min

## MATHEMATICAL MODELLING

- The parameter estimation procedure was based on the minimization of residual error between model calculations and experimental data (weight loss,  $P$ , versus temperature,  $T$ , data).
- An objective function which is the accumulated residual error between experimental data and model prediction is introduced and is the optimisation aim.
- The manipulated variables (MVs) for this optimization problem will be the parameters that the model aims to determine.
- The constrained non-linear multivariable optimization method was used to set the boundary conditions for conversion factors  $f$  to be between 0% and 100%. Microsoft Excel Solver® was used as the optimization routine to determine the model parameters.
- This optimization package was based on the Generalized Reduced Gradient (GRG2) implementation that can handle non-linear models as well as variable constraints.

# MATHEMATICAL MODELLING – Solver Flowchart

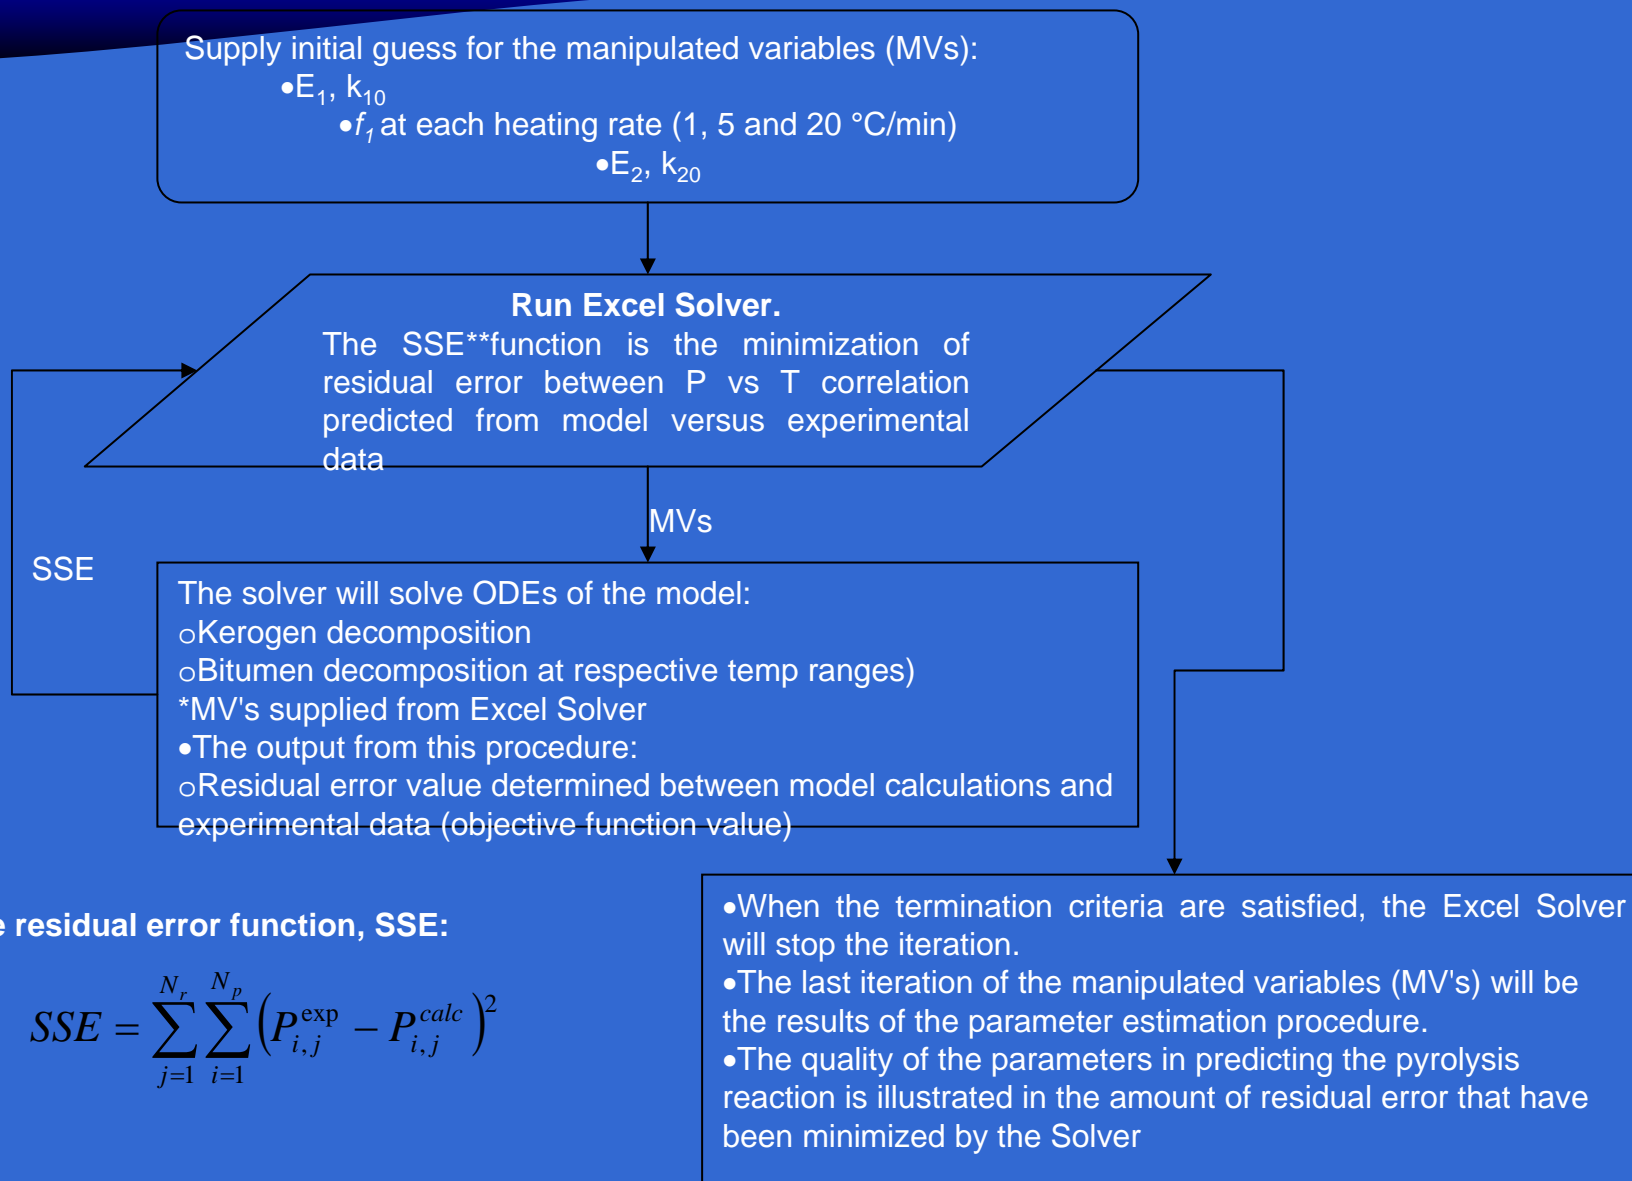



## PRESENTATION OUTLINE

 Introduction to Malaysia

Methodology




**Results & Future Studies**

Questions



# RESULTS

1	T (deg C)	1 deg C/min	T (deg C)	5 deg C/min	T (deg C)	20 deg C/min
2	300	100	300	100	325	100
3	325	99.3853321	325	99.77479111	350	99.83050799
4	350	98.3991193	350	99.32063711	375	99.49921585
5	375	97.28879341	375	98.5089658	400	98.90219337
6	400	96.58606259	400	97.27941776	425	97.92592855
7	425	95.81448118	425	95.81860526	450	96.51912508
8	450	94.78381072	450	95.6322457	475	96.44927864
9	475	93.45295385	475	95.38275728	500	96.35704495
10	500	91.79337874	500	95.05627251	525	96.23751581
11	525	89.79825062	525	94.63816208	550	96.08527792
12	550	87.49154141	550	94.11372545	575	95.89448335
13			575	93.46911413	600	95.65895179
14						
15						
16						
17						
18						
19						
20						
21						
22						
23						
24						
25						
26						
27						
28						
29						
30						
31						
32						
33						
34						
35						
36						
37						
38						
39						
40						
41						
42						
43						

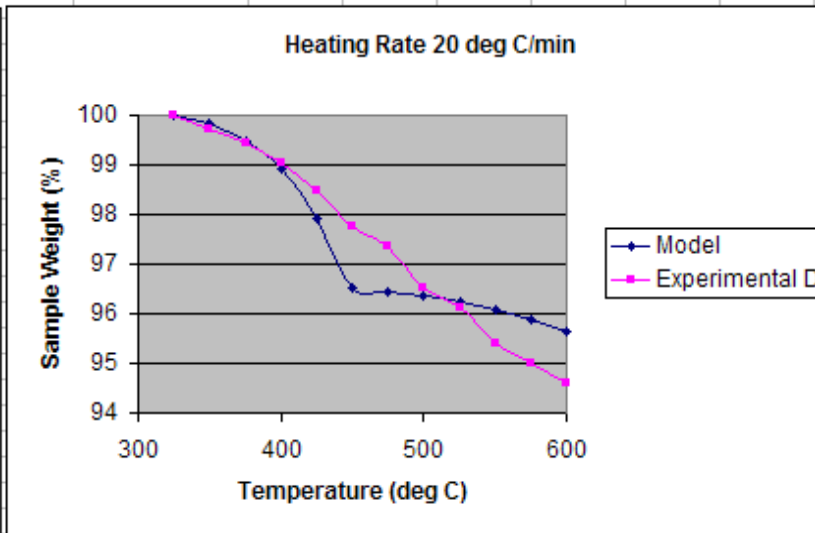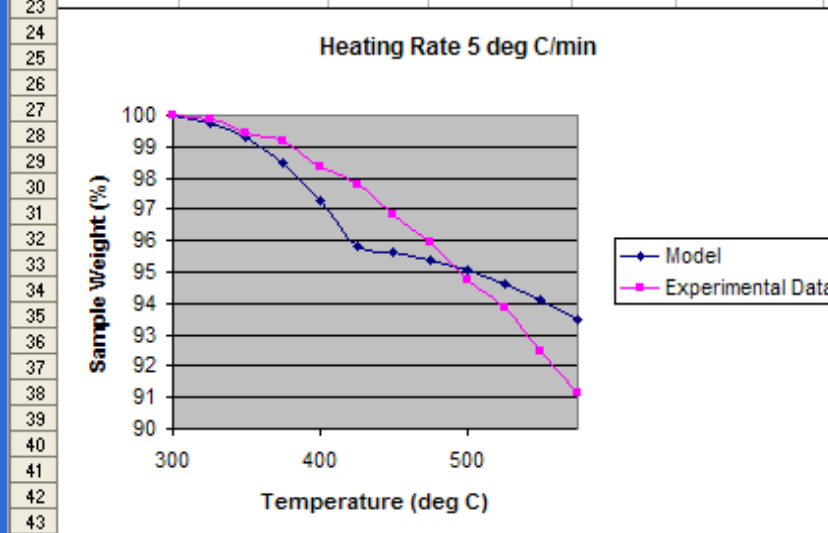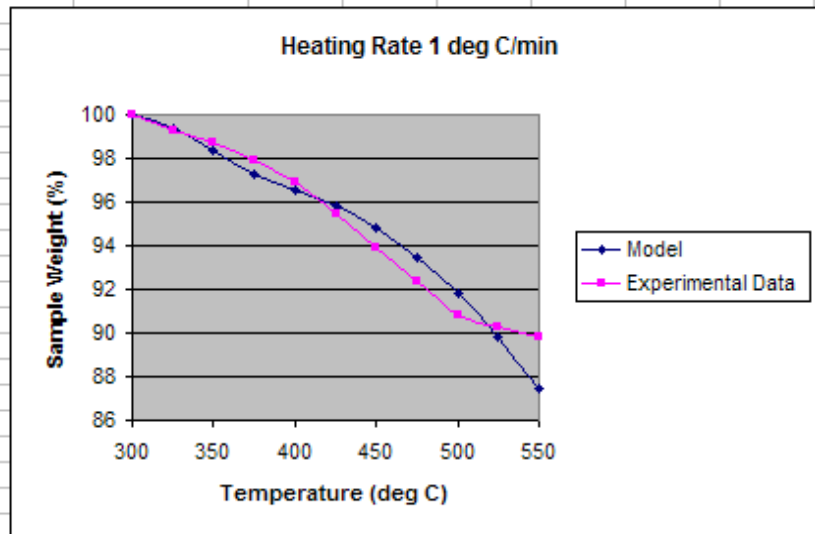


# Results Summary

<i>Model parameters</i>	<i>Initial guess</i>	<i>Final value</i>
$E_1$ (J/mol)	$77.70 \times 10^3$	$9.08 \times 10^4$
$k_{10}$	$2.80 \times 10^4$	$8.19 \times 10^5$
$E_2$ (J/mol)	$116.20 \times 10^3$	$4.63 \times 10^5$
$k_{20}$	$4.80 \times 10^5$	$1.08 \times 10^6$
$f_i$ @ 1 °C/min	0.21	0.36
$f_i$ @ 5 °C/min	0.24	0.39
$f_i$ @ 20 °C/min	0.32	0.41
Sum of residual error (SSE)	$2.41 \times 10^{-2}$	$3.57 \times 10^{-3}$

Summary of initial value provided compared to final value obtained

Chart comparing experimental results versus model results for heating rate of 1°C/min

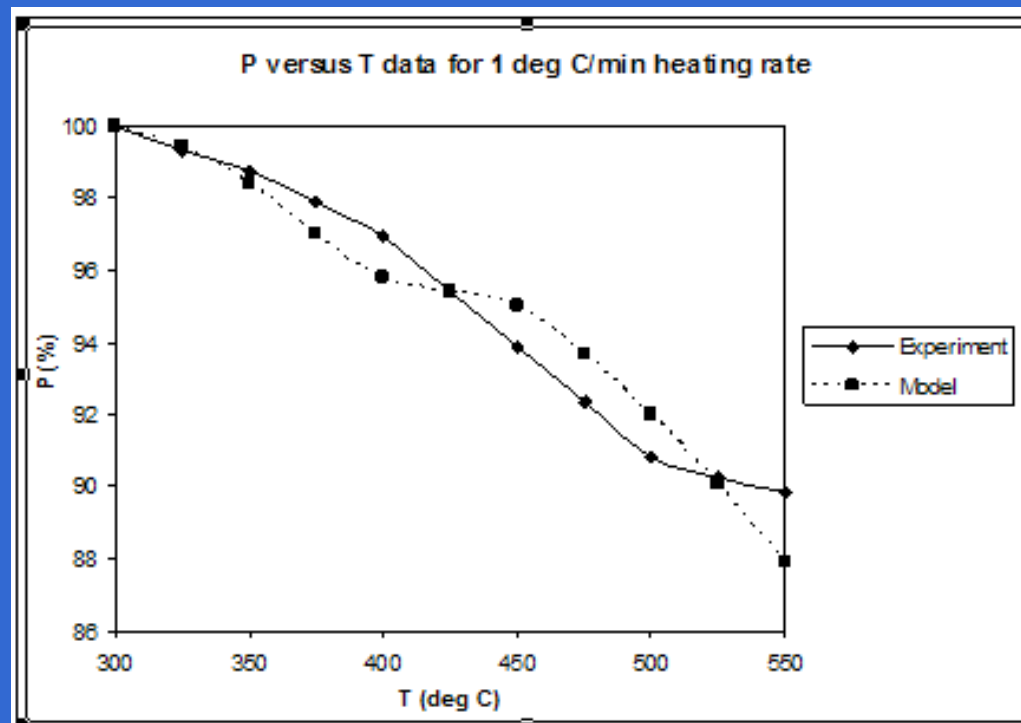

# Results Summary



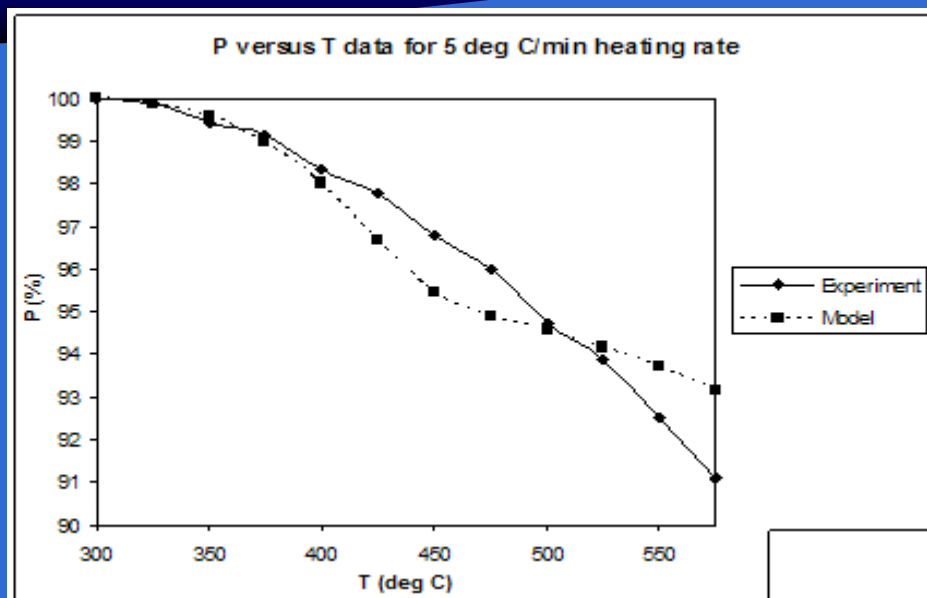


Chart comparing experimental results versus model results for heating rate of 5°C/min

Chart comparing experimental results versus model results for heating rate of 20°C/min

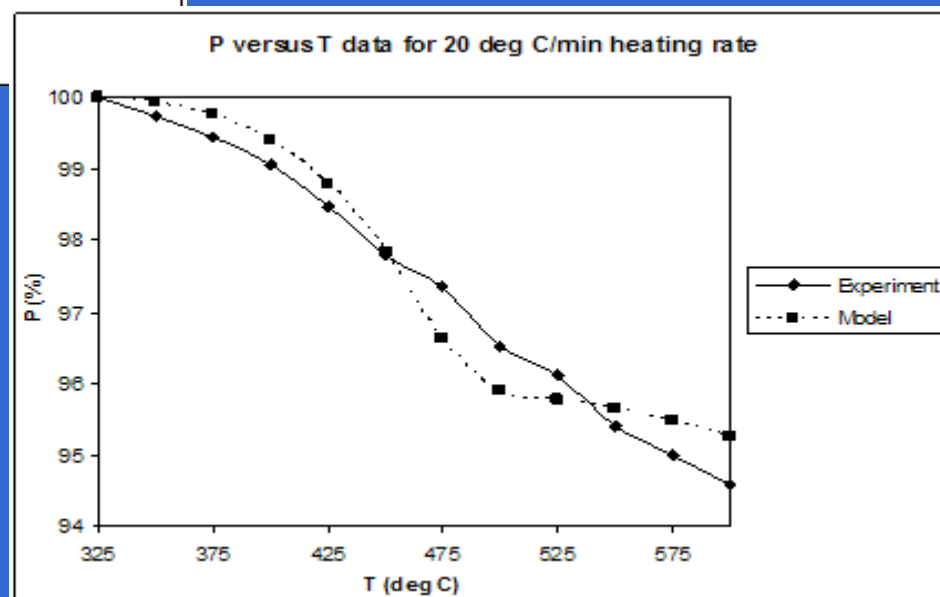

## Results Summary

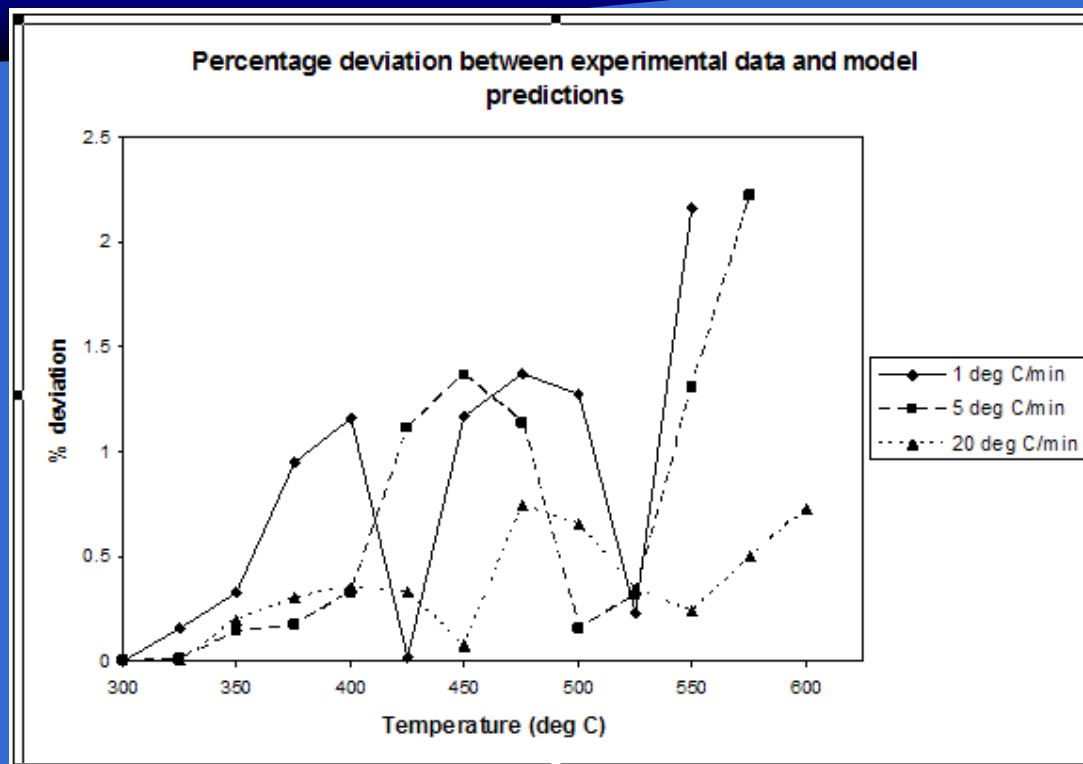

- Predicted P vs T curve matches reasonably well with the trend observed from the non-isothermal TGA experiment.
- However error is consistent.

- Possible sources of errors:
  - Accuracy of the experimental results
  - The presence of many local solutions to the given problem will make the effort to determine the most accurate value of the model parameters difficult as the methodology adopted to determine the model parameters was a nonlinear optimization problem

## Model Results Summary


- Methods that can be applied to improve results:
  - Including additional terms in the model formulation can increase the capability of the model to predict the decomposition process of the oil shale sample and enhance model accuracy. (Model accuracy is reflected in the ability to make good predictions that agree with experimental observations)
  - Utilizing more accurate apparatus and improving the experimental procedure.
  - Validate results using various sets of oil shale sample data and improving the experimental data estimation
  - Numerical data from more extensive TGA analysis or other experimental analyses, which could provide sufficient and accurate data
  - Numerical analysis of this sample maintains the prediction of oil and gas formation on the basis of heating regardless of the retorting technique used.
- TGA analysis limitation:
  - The inability to characterize the oil and gas into detailed chemical composition
  - Should be improved to include the presence of hydro-cracking and hydro-coking reactions.
  - Unable to determine detailed compositional analysis of final or intermediate products

## CONCLUSION

- The oil shale decomposition reaction that derives a set of ODEs can be solved using numerical methods. Focus on fourth order Runge-Kutta method which will provide the parameters of the reaction kinetics.
- The result of the model using the Runge-Kutta method as compared to experimental data from previous studies was reasonably accurate with a maximum deviation of 2.3%.
- Oil cracking and coking reactions occurring along with the oil shale decomposition were not included in this kinetics study due to TGA limitations
- The model can be used as a tool to predict oil and gas production capacity for given shale sample.
- Future studies will include variations to the experimental methodology to:
  - ensure increased accuracy
  - better represent the oil shale decomposition process
  - assist in better understanding oil shale decomposition kinetics from any source and potentially improve productivity in the areas of oil shale production

## WAY FORWARD



- Introduce the concept of oil upgrading for future studies to:
- Better understand the upgrading requirements of the oil shale products.
- The first aspect would be the differentiation between the substances composing the vapor phase product (oil, gas and water).

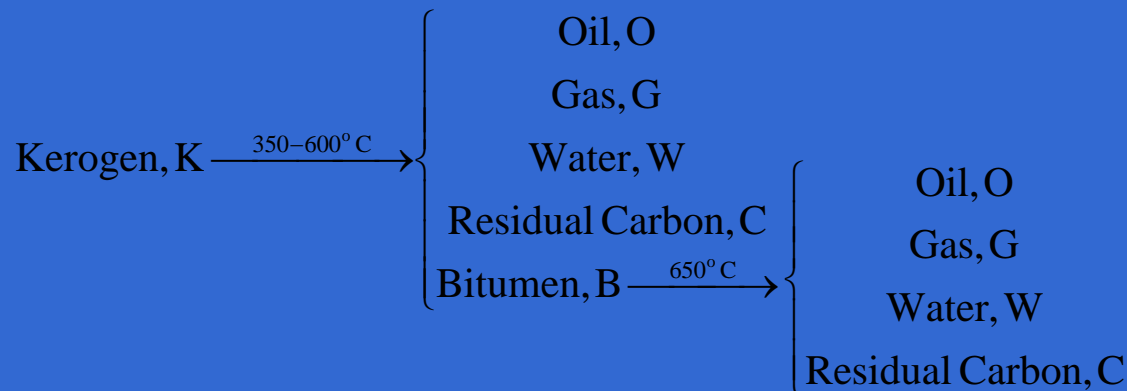

- The above equation represents a slightly detailed composition differentiation of the kerogen and bitumen decomposition products.
- The ability to consistently quantify these substances in an experiment would allow a more comprehensive and detailed modeling for the decomposition reactions.

## WAY FORWARD

- The other aspect would be modeling of cracking and coking reactions. This reaction set can be described in four generalized reactions:



- Note that each of these components can be further characterized into detailed chemical substances with more comprehensive experimental methodologies such as IR spectroscopy and gas chromatography.
- Acquiring these data in future studies through detailed experimentation would allow a more rigorous and detailed analysis to be modeled.
- Future work would also include studying kinetics of the detailed reactions to be incorporated into the model as well as justifying the model with other numerical methods to determine solutions to the ODEs



Thank You



## PRESENTATION OUTLINE



Introduction to Malaysia

PETRONAS – An Overview

Shale Oil Modeling

Questions



# TGA DATA

Weight loss vs. Temperature at different heating rates

Scale	Heating rates (°C/min)										
	180		1		5		20				
	%	mm	mm	%	mm	%	mm	%	mm	%	
7											
8	50										
9		T °C									
10											
11		300.0	1	0.0	100.0	1	0.0	100.0	1	0.0	100.0
12		325.0	2	2.5	99.3	2	0.5	99.9	1	0.0	100.0
13		350.0	3	4.5	98.8	3	2.0	99.4	2	1.0	99.7
14		375.0	4	7.5	97.9	4	3.0	99.2	3	2.0	99.4
15		400.0	5	11.0	96.9	5	6.0	98.3	4	3.4	99.1
16		425.0	6	16.5	95.4	6	8.0	97.8	5	5.5	98.5
17		450.0	7	22.0	93.9	7	11.5	96.8	6	8.0	97.8
18		475.0	8	27.5	92.4	8	14.5	96.0	7	9.5	97.4
19		500.0	9	33.0	90.8	9	19.0	94.7	8	12.5	96.5
20		525.0	10	35.0	90.3	10	22.0	93.9	9	14.0	96.1
21		550.0	11	36.5	89.9	11	27.0	92.5	10	16.5	95.4
22		575.0	12	38.0	89.4	12	32.0	91.1	11	18.0	95.0
23		600.0	13	40.0	88.9	13	35.0	90.3	12	19.5	94.6
24		625.0	14	43.0	88.1	14	37.5	89.6	13	22.0	93.9
25		650.0	15	51.0	85.8	15	41.0	88.6	14	24.0	93.3
26		675	16	63.5	82.4	16	44.5	87.6	15	27.0	92.5
27		700	17	85.0	76.4	17	52.0	85.6	16	31.0	91.4
28		725	18	108.5	69.9	18	65.0	81.9	17	35.5	90.1
29		750	19	113.5	68.5	19	83.0	76.9	18	40.0	88.9
30		775				20	102.5	71.5	19	50.0	86.1
31		800				21	102.5	71.5	20	65.0	81.9
32		825							21	85.0	76.4
33		850							22	105.0	70.8
34		875							23	107.0	70.3
35		900							24	108.5	69.9
36		925							25	109.0	69.7
37		950							26	109.0	69.7
38		975							27	109.5	69.6
39		1000							28	109.5	69.6

